

Research



Cite this article: Su Y, Riccobelli D, Chen Y, Chen W, Ciarletta P. 2023 Tunable morphing of electroactive dielectric-elastomer balloons.

Proc. R. Soc. A **479**: 20230358.

<https://doi.org/10.1098/rspa.2023.0358>

Received: 22 May 2023

Accepted: 17 July 2023

Subject Areas:

mathematical modelling, mechanics

Keywords:

dielectric elastomer, buckling, snap-through instability, finite-element method

Authors for correspondence:

Weiqiu Chen

e-mail: chenwq@zju.edu.cn

Pasquale Ciarletta

e-mail: pasquale.ciarletta@polimi.it

[†]These authors contributed equally to the study.

Electronic supplementary material is available online at <https://doi.org/10.6084/m9.figshare.c.6764173>.

Tunable morphing of electroactive dielectric-elastomer balloons

Yipin Su^{1,†}, Davide Riccobelli^{1,†}, Yingjie Chen^{2,†}, Weiqiu Chen^{2,3} and Pasquale Ciarletta¹

¹MOX—Dipartimento di Matematica, Politecnico di Milano, Piazza Leonardo da Vinci 32, Milan 20133, Italy

²Department of Engineering Mechanics, Zhejiang University, Hangzhou 310027, People's Republic of China

³Shenzhen Research Institute of Zhejiang University, Shenzhen 518057, People's Republic of China

DR, 0000-0001-6424-5689; PC, 0000-0002-1011-5587

Designing smart devices with tunable shapes has important applications in industrial manufacture. In this paper, we investigate the nonlinear deformation and the morphological transitions between buckling, necking and snap-through instabilities of layered dielectric elastomer (DE) balloons in response to an applied radial voltage and an inner pressure. We propose a general mathematical theory of nonlinear electro-elasticity able to account for finite inhomogeneous strains provoked by the electro-mechanical coupling. We investigate the onsets of morphological transitions of the spherically symmetric balloons using the surface impedance matrix method. Moreover, we study the nonlinear evolution of the bifurcated branches through finite-element numerical simulations. Our analysis demonstrates the possibility to design tunable DE spheres, where the onset of buckling and necking can be controlled by geometrical and mechanical properties of the passive elastic layers. Relevant applications include soft robotics and mechanical actuators.

1. Introduction

Dielectric elastomers (DEs) are soft smart materials capable of performing large deformations in fast response to electrical stimuli. In the last decades, they have attracted considerable attention, from both

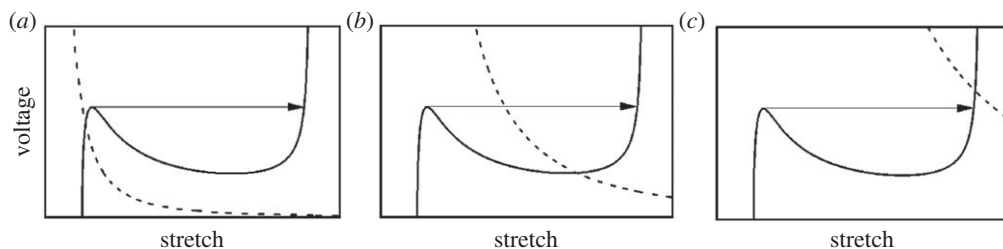


Figure 1. Nonlinear responses of planar DE actuators subject to a voltage through the thickness: (a) electrical breakdown occurs prior to the onset of snap-through instability (type I); (b) snap-through instability induces electrical breakdown of the material (type II); and (c) the DEs survive the snap-through instability (type III). The solid and dashed curves correspond to the voltage-stretch loading curve and the electric breakdown curve of the materials, respectively. The arrow represents the snap-through path of the material during the deformation.

academia and industry, for many applications at the core of modern technologies, such as soft robots, artificial muscles, actuators and energy harvesters [1,2]. A typical DE actuator consists of a soft elastomer sandwiched between two compliant electrodes. The actuator deforms when subject to a voltage along the thickness direction, accompanied by a reduction in the thickness and an expansion in the area [3,4]. The DE balloon is widely used as a device configuration for its suitability to enhance the electric-induced deformation and for its versatility in industrial applications [5,6]. In some practical applications, the DE devices should be insulated from their surroundings. For example, a wearable device is capable of delivering haptic information by adding a soft elastic insulation layer outside the DE actuator, protecting human skin, enhancing breathability and preventing slippage [7].

A clear advantage of using DEs is the N-shaped constitutive curve between the applied voltage and the resulting stretch, which characterizes the so-called *snap-through instability* [8,9]. It consists of a sudden increase of the resulting strain as the applied voltage reaches the local maximum value, as presented in figure 1. Taking advantage of this feature, a giant areal strain can be obtained, as large as 1600% [10,11].

Due to their geometric and constitutive nonlinearities, as well as to the multi-physics coupling, DE devices can be modelled as boundary value problems (BVPs) that are generally difficult to solve. Multiple morphological transitions can occur due to the presence of many stationary points of the electro-mechanical functional of interest. For instance, necking (i.e. the local thinning of an elastic body under tension) was initially identified as a precursor of structural failure of DE devices, which should be avoided [12]. On the contrary, more recent studies have reported that compressive buckling can be positively used to control shape and surface patterns in functional devices and biological tissues [13,14].

In this respect, the buckling of nonlinear elastic, thick-walled balloons has been extensively studied in the past [15–17]. So far, some efforts have been devoted in the literature to the study of mechanical behaviours of DE balloons. For example, Alibakhshi *et al.* [18] studied the nonlinear vibration and stability of a dielectric-elastomer balloon based on a strain-stiffening model. Jin & Huang [19] investigated the random response of dielectric elastomer balloons disturbed by electrical or mechanical fluctuation. Sharma *et al.* developed an energy-based method for estimating the dynamic pull-in instability parameters of the DE balloon actuator undergoing homogeneous deformation in [20]. Liang & Cai [21] proposed a study of shape bifurcation of a spherical dielectric-elastomer balloon subject to internal pressure and electric voltage. Xie *et al.* [22] studied the bifurcation of a dielectric elastomer balloon under pressurized inflation and electric actuation. Rudykh *et al.* [23] investigated the response of electroactive balloons subject to coupled electro-mechanical stimuli. The inflation deformation of an electro-elastic spherical shell subject to an internal pressure and a radial voltage was examined in [24]. Mao *et al.*

[25] conducted a three-dimensional analytical study of the small-amplitude free vibration of a SEA spherical balloon with radially inhomogeneous biasing fields. The bifurcation of finitely deformed thick-walled electro-elastic spherical shells subject to a radial electric field was analysed in [26]. It should be noted that most existing works focused on monolayer DE balloons. Recently, layered dielectric composites have gained more and more attention. Osman *et al.* proposed the approaches for preparing bi-layered polydimethylsiloxane composite for dielectric elastomer applications. Kumar *et al.* [27] theoretically studied the dynamic electromechanical behaviour of multi-layered DE composites. Su *et al.* [28] proposed a dielectric-elastomer bilayer capable of smart bending deformation. Four different criteria of multi-layered soft dielectrics under plane-strain conditions were compared in [29]. To the best knowledge of the authors, the only related work on the nonlinear response of multi-layered DE balloons was proposed by Bortot [6]. However, the influences of the layered configuration and the applied electro-mechanical stimuli on the morphological diagram of layered DE balloons are still unknown. By analysing the electroelastic behaviour of a spherical piezoceramic sensor coated by a homogeneous protective layer, it was shown that the existence of the protective layer can prolong the effective working life of the piezoceramic sensor [30]. It is unclear whether or not this enhancement can happen in dielectric devices.

Here, we propose a theoretical and numerical study of an incompressible layered dielectric-elastic balloon subject to the combined action of electrical and mechanical loads. For simplification, we only consider type III DEs as defined in figure 1c, excluding the possibility of electric breakdown of the material before the onsets of the snap-through and the necking instabilities. We investigate the possibility to enhance and to control the electric-induced deformation field by coating an inactive elastic layer outside the DE balloon.

The article is structured as follows. In §2, we derive the governing equations for the inflation of a layered dielectric-elastic balloon subject to an internal pressure and a radial voltage. We assume that the elastic and DE layers are perfectly bonded. In §3, we formulate the linear stability analysis of the radially symmetric solution, using the surface impedance matrix method to implement a robust numerical scheme for solving the linearized BVP for a generic constitutive function. In §4a, we illustrate the solution obtained by assuming a Gent constitutive response. In §4b, we compare the numerical results obtained for elastic monolayer, DE monolayer and bi-layered dielectric-elastic balloons. In §5, we present a post-buckling analysis of the devices by means of a finite-element approximation of the nonlinear problem. In §6, we finally discuss the relevance of our results for enabling a novel design strategy for tuning shapes of DE devices, together with a few concluding remarks.

2. The electro-mechanical model

In this section, we define the nonlinear BVP describing the response of a spherical dielectric-elastic balloon to electro-mechanical stimuli, deriving its radially symmetric solution.

(a) Nonlinear boundary value problem

Let us consider a thick-walled bi-layered spherical balloon that occupies the domain $\mathcal{B}_0 \subset \mathbb{R}^3$ in its reference configuration. Specifically $\mathcal{B}_0 = \mathcal{B}_0^d \cup \mathcal{B}_0^e$, where

$$\left. \begin{aligned} \mathcal{B}_0^d &= \{\mathbf{X} \in \mathbb{R}^3 | R_i < \|\mathbf{X}\| \leq R_m\} \\ \mathcal{B}_0^e &= \{\mathbf{X} \in \mathbb{R}^3 | R_m < \|\mathbf{X}\| \leq R_o\}, \end{aligned} \right\} \quad (2.1)$$

and

as illustrated in figure 2. We assume that the inner and outer layers are made of DE and elastic elastomers, respectively. Throughout the paper, we denote the quantities related to the inner, interfacial and outer surfaces by the subscripts $(\bullet)_i$, $(\bullet)_m$ and $(\bullet)_o$, respectively, and the quantities related to the DE and elastic layers by the superscripts $(\bullet)^d$ and $(\bullet)^e$, respectively. $\mathbf{X}$ and $\mathbf{x} = \chi(\mathbf{X})$ are the reference and the actual position vectors, respectively, with $\chi : \mathcal{B}_0 \rightarrow \mathbb{R}^3$ being the mapping

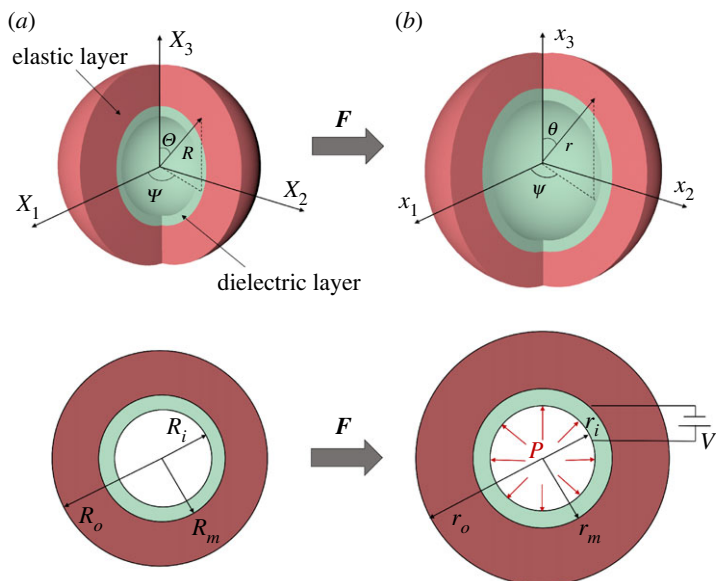


Figure 2. Sketch of a layered dielectric-elastic balloon subject to a radial voltage V through the DE layer and an internal pressure P at the inner surface: (a) undeformed and (b) deformed configurations. The upper row depicts the three-dimensional domains with the respective spherical coordinate systems, and the lower row shows the corresponding in-plane cross sections with geometrical and electro-mechanical loading parameters.

from the reference configuration to the actual configuration $\mathcal{B} = \chi(\mathcal{B}_0)$. Then the displacement field is $\mathbf{u} = \mathbf{x} - \mathbf{X}$.

Let $(\mathbf{e}_R, \mathbf{e}_\Psi, \mathbf{e}_\Theta)$ and $(\mathbf{e}_r, \mathbf{e}_\psi, \mathbf{e}_\theta)$ be the corresponding spherical orthonormal bases in the reference and actual configurations, respectively. Moreover, let (R, Ψ, Θ) and (r, ψ, θ) be the spherical coordinates in the reference and actual frames, respectively, so that

$$\left. \begin{aligned} \mathbf{X} &= (X_1, X_2, X_3) = (R \sin \Theta \cos \Psi, R \sin \Theta \sin \Psi, R \cos \Theta) \\ \text{and} \quad \mathbf{x} &= (x_1, x_2, x_3) = (r \sin \theta \cos \psi, r \sin \theta \sin \psi, r \cos \theta). \end{aligned} \right\} \quad (2.2)$$

We denote by $\mathbf{F} = \text{Grad } \chi$ the deformation gradient, where Grad is the material gradient operator. In the following, we use capital letters for all the differential operators referring to the reference frame. We assume that both layers are incompressible, so that everywhere holds the constraint

$$\det \mathbf{F} = 1. \quad (2.3)$$

We now introduce the true electric field $\mathbf{E} : \mathcal{B} \rightarrow \mathbb{R}^3$ and the true electric displacement field $\mathbf{D} : \mathcal{B} \rightarrow \mathbb{R}^3$. Their Lagrangian counterparts are given by

$$\mathbf{E}_L = \mathbf{F}^T \mathbf{E} \quad \text{and} \quad \mathbf{D}_L = \mathbf{F}^{-1} \mathbf{D}. \quad (2.4)$$

Accordingly, the Maxwell equations in the material frame read

$$\text{Curl } \mathbf{E}_L = \mathbf{0} \quad \text{and} \quad \text{Div } \mathbf{D}_L = 0, \quad (2.5)$$

or, equivalently, in the spatial setting

$$\text{curl } \mathbf{E} = \mathbf{0} \quad \text{and} \quad \text{div } \mathbf{D} = 0, \quad (2.6)$$

where div and curl are the spatial divergence and curl operators, respectively, and Div and Curl their material counterparts. The first equation is automatically satisfied if we introduce the electric

potential ϕ such that:

$$\mathbf{E} = -\text{grad } \phi. \quad (2.7)$$

Both in $\mathcal{B}_0^d$ and in $\mathcal{B}_0^e$, the nominal stress $\mathbf{S}$ must satisfy the balance equation

$$\text{Div } \mathbf{S} = \mathbf{0}, \quad (2.8)$$

while we require that the normal traction and displacement are continuous at the interface between the elastomer and the dielectric layers, that is

$$\lim_{R \rightarrow R_m^-} \mathbf{S}^T \mathbf{e}_R = \lim_{R \rightarrow R_m^+} \mathbf{S}^T \mathbf{e}_R. \quad (2.9)$$

We postulate the existence of an energy density W in the form

$$W = \begin{cases} W^d(\mathbf{F}, \mathbf{D}_L) & \text{in } \mathcal{B}_0^d, \\ W^e(\mathbf{F}) & \text{in } \mathcal{B}_0^e. \end{cases} \quad (2.10)$$

The DE is assumed to be isotropic. In virtue of the representation theorem of isotropic functions, the energy density can be generally written as a function of five invariants, namely $W^d = W^d(I_1, I_2, I_4, I_5, I_6)$, where

$$I_1 = \text{tr } \mathbf{C}, \quad I_2 = \frac{I_1^2 - \text{tr}(\mathbf{C}^2)}{2}, \quad I_4 = \mathbf{D}_L \cdot \mathbf{D}_L, \quad I_5 = \mathbf{D}_L \cdot \mathbf{C} \mathbf{D}_L, \quad I_6 = \mathbf{D}_L \cdot \mathbf{C}^2 \mathbf{D}_L, \quad (2.11)$$

where $\mathbf{C}$ is the right Cauchy–Green tensor, given by $\mathbf{C} = \mathbf{F}^T \mathbf{F}$. The elastomer is also isotropic and therefore $W^e = W^e(I_1, I_2)$.

By standard thermo-mechanical considerations [31], the nominal stress and the Lagrangian electric field can be expressed as

$$\mathbf{S} = \frac{\partial W}{\partial \mathbf{F}} - p \mathbf{F}^{-1} \quad \text{and} \quad \mathbf{E}_L = \frac{\partial W}{\partial \mathbf{D}_L}, \quad (2.12)$$

where p is a Lagrange multiplier that enforces the incompressibility constraint (2.3). For later convenience, we also introduce the push-forward of the nominal stress in the actual configuration, i.e. the Cauchy stress tensor

$$\mathbf{T} = \mathbf{F} \mathbf{S}. \quad (2.13)$$

The Maxwell equation (2.5) and the balance equation (2.8) are complemented by interface and boundary conditions. We assume that the inner and the outer surfaces of the DE layer are coated with compliant electrodes, so that the potential difference between the surfaces of the dielectric is a fixed applied voltage V , namely

$$\Delta \phi = \phi(R_m) - \phi(R_i) = V. \quad (2.14)$$

Furthermore, we assume that the inner surface of the bilayer is subject to a pressure P , such that

$$\mathbf{S}^T \mathbf{N} = -P \mathbf{F}^{-T} \mathbf{N}, \quad (2.15)$$

where $\mathbf{N}$ is the outward normal vector.

In the following, we derive the radially symmetric solution of the BVP given by equations (2.3)–(2.15).

(b) Radially symmetric solution

We look for a particular solution of the BVP using the ansatz

$$r = r(R), \quad \theta = \Theta, \quad \psi = \Psi \quad \text{and} \quad \phi = \phi(R). \quad (2.16)$$

We introduce the spatial inner, interfacial and outer radii $r_i = r(R_i)$, $r_m = r(R_m)$ and $r_o = r(R_o)$, respectively. Using spherical coordinates, the deformation gradient reads

$$\begin{aligned} \mathbf{F} &= \lambda_r \mathbf{e}_r \otimes \mathbf{E}_R + \lambda_\theta \mathbf{e}_\theta \otimes \mathbf{E}_\Theta + \lambda_\psi \mathbf{e}_\psi \otimes \mathbf{E}_\Psi \\ &= \frac{dr}{dR} \mathbf{e}_r \otimes \mathbf{E}_R + \frac{r}{R} (\mathbf{e}_\theta \otimes \mathbf{E}_\Theta + \mathbf{e}_\psi \otimes \mathbf{E}_\Psi), \end{aligned} \quad (2.17)$$

where λ_j ($j = r, \theta, \psi$) is the stretch at j -direction of the balloon.

Using the incompressibility assumption (2.3) in its local and global forms, we get

$$\frac{dr}{dR} \frac{r^2}{R^2} = 1 \implies r(R) = \sqrt[3]{R^3 - R_i^3 + r_i^3}. \quad (2.18)$$

We denote the hoop stretch as $\lambda = r/R$, so that

$$\lambda_r = \frac{1}{\lambda^2} \quad \text{and} \quad \lambda_\theta = \lambda_\psi = \lambda. \quad (2.19)$$

From equation (2.18), the following relationships hold between the stretches at the inner, interfacial and outer surfaces $\lambda_i = r_i/R_i$, $\lambda_m = r_m/R_m$ and $\lambda_o = r_o/R_o$ of the balloon,

$$\lambda_m = [1 + (t^d)^3(\lambda_i^3 - 1)]^{1/3} \quad \text{and} \quad \lambda_o = [1 + (t^e)^3(\lambda_m^3 - 1)]^{1/3}, \quad (2.20)$$

where $t^d = R_i/R_m$ and $t^e = R_m/R_o$ are the aspect ratios of the DE and elastic layers, respectively. We remark that the limit cases $t^d \rightarrow 1$ and $t^e \rightarrow 1$ correspond to monolayer elastic and DE balloons, respectively.

The radial electric field generated by the applied potential difference V only exists in the DE layer. According to our ansatz, the nominal electric field and nominal electric displacement have the forms

$$\mathbf{E}_L = E_R \mathbf{e}_R \quad \text{and} \quad \mathbf{D}_L = D_R \mathbf{e}_R, \quad (2.21)$$

where E_R and D_R are the only non-zero components of the nominal electric field and nominal electric displacement, respectively. The corresponding true electric field and true electric displacement are

$$\mathbf{E} = \mathbf{F}^{-T} \mathbf{E}_L = E_r \mathbf{e}_r \quad \text{and} \quad \mathbf{D} = \mathbf{F} \mathbf{D}_L = D_r \mathbf{e}_r, \quad (2.22)$$

where $E_r = \lambda^2 E_R$ and $D_r = \lambda^{-2} D_R$ are the only non-zero components of the true electric field and true electric displacement, respectively.

From equations (2.11) and (2.19), we obtain the following expressions of the invariants

$$I_1 = 2\lambda^2 + \lambda^{-4}, \quad I_2 = 2\lambda^{-2} + \lambda^4, \quad I_4 = D_R^2, \quad I_5 = \lambda^{-4} D_R^2 \quad \text{and} \quad I_6 = \lambda^{-8} D_R^2. \quad (2.23)$$

By using equation (2.12)₂, we get

$$E_r = 2(\lambda^2 W_4^d + W_5^d + \lambda^{-6} W_6^d) D_R, \quad (2.24)$$

where $W_j^s = \partial W^s / \partial I_j$, with $s = (d, e)$.

The only non-zero components of the Cauchy stress in spherical coordinates are given by

$$\left. \begin{aligned} T_{rr}^d &= 2[\lambda^{-4}W_1^d + 2\lambda^{-2}W_2^d + (\lambda^{-4}W_5^d + 2\lambda^{-8}W_6^d)D_R^2] - p^d \\ T_{\theta\theta}^d &= T_{\psi\psi}^d = 2[\lambda^2W_1^d + (\lambda^{-2} + \lambda^4)W_2^d] - p^d, \end{aligned} \right\} \quad (2.25)$$

in the DE layer, and

$$\left. \begin{aligned} T_{rr}^e &= 2(\lambda^{-4}W_1^e + 2\lambda^{-2}W_2^e) - p^e \\ T_{\theta\theta}^e &= T_{\psi\psi}^e = 2[\lambda^2W_1^e + (\lambda^{-2} + \lambda^4)W_2^e] - p^e, \end{aligned} \right\} \quad (2.26)$$

in the elastic layer. Here p^s , where $s=d,e$, is a Lagrange multiplier associated with the incompressibility constraint of the s th layer, which will be determined from the equilibrium equations and boundary conditions as detailed in the following.

The balance equation (2.8) in the actual configuration imposes

$$\operatorname{div} \mathbf{T} = \mathbf{0}. \quad (2.27)$$

Under the symmetry assumption made in equations (2.16) and (2.5)₂ becomes

$$\frac{1}{r^2} \frac{\partial(r^2 D_r)}{\partial r} = 0, \quad (2.28)$$

which implies that $r^2 D_r$ is a constant, and equation (2.27) reads

$$\frac{\partial T_{rr}^s}{\partial r} = \frac{2}{r} (T_{\theta\theta}^s - T_{rr}^s) \quad (s = d, e). \quad (2.29)$$

By introducing the reduced energy functions defined by

$$W_{\text{sph}}^d(\lambda, D_R) = W^d(I_1, I_2, I_4, I_5, I_6) \quad \text{and} \quad W_{\text{sph}}^e(\lambda) = W^e(I_1, I_2), \quad (2.30)$$

and by substituting equations (2.23), (2.24) and (2.30), we have

$$E_r = \lambda^2 \frac{\partial W_{\text{sph}}^d}{\partial D_R}. \quad (2.31)$$

Accordingly, the applied voltage is

$$V = \int_{r_i}^{r_m} \lambda^2 \frac{\partial W_{\text{sph}}^d}{\partial D_R} dr. \quad (2.32)$$

Similarly, equation (2.29) can be rewritten compactly as

$$\frac{\partial T_{rr}^s}{\partial r} = \frac{\lambda}{r} \frac{\partial W_{\text{sph}}^s}{\partial \lambda} \quad (s = d, e). \quad (2.33)$$

Using the boundary conditions

$$T_{rr}^d(r_i) = -P \quad \text{and} \quad T_{rr}^e(r_o) = 0, \quad (2.34)$$

and equation (2.33), the principal stresses in the radial direction read

$$\left. \begin{aligned} T_{rr}^d &= \int_{\lambda_i}^{\lambda} \frac{1}{1-\lambda^3} \frac{\partial W_{\text{sph}}^d}{\partial \lambda} d\lambda - P \quad \text{in the DE layer} \\ T_{rr}^e &= \int_{\lambda_o}^{\lambda} \frac{1}{1-\lambda^3} \frac{\partial W_{\text{sph}}^e}{\partial \lambda} d\lambda \quad \text{at the elastic layer.} \end{aligned} \right\} \quad (2.35)$$

Note that we have used the following relationship

$$\frac{dr}{r} = \frac{d\lambda}{\lambda(1-\lambda^3)}, \quad (2.36)$$

which can be obtained from equations (2.18) and (2.19).

The hoop stresses $T_{\theta\theta}^s = T_{\psi\psi}^s$ can be determined using the following relationship

$$2(T_{\theta\theta}^s - T_{rr}^s) = \lambda \frac{\partial W_{\text{sph}}^s}{\partial \lambda} \quad (s = d, e), \quad (2.37)$$

which results from equations (2.29) and (2.33).

The two layers are perfectly bonded to each other, imposing the continuity of the displacements and normal stresses at the interface, see equation (2.9). As a result, the relationship between λ_i , λ_m , λ_o and V can be established, using equation (2.35), as

$$\int_{\lambda_i}^{\lambda_m} \frac{1}{1 - \lambda^3} \frac{\partial W_{\text{sph}}^d}{\partial \lambda} d\lambda - P = \int_{\lambda_o}^{\lambda_m} \frac{1}{1 - \lambda^3} \frac{\partial W_{\text{sph}}^e}{\partial \lambda} d\lambda. \quad (2.38)$$

Finally, the deformation λ_i , λ_m and λ_o can be fully determined from equations (2.20), (2.32) and (2.38), once the inner pressure P , voltage V and constitutive laws W^s , with $s = (d, e)$, are given.

3. Linear stability analysis

Mechanical instabilities may occur in finitely deformed solids, and the onset of buckling and necking can be predicted by using the theory of incremental deformations superposed on a finite strain [25,32–35]. In this section, we derive the governing equations for the analysis of small-amplitude wrinkles superimposed upon the finite deformation of the balloon, and develop the surface impedance matrix method applicable to layered structures to build a robust numerical procedure for solving the resulting dispersion equations. Here we just give the general governing equations of the deformed DE elastomer, and we omit the superscript for the sake of notation compactness. Note that the incremental governing equations for the elastic elastomer can be simply derived by making the electric field vanish in the given solution.

(a) Incremental BVP

Due to the spherical symmetry, the study of axisymmetric modes is sufficient to give a full insight into the buckling behaviour of the material, since the dependence on ψ does not alter the incremental BVP [15]. Let us superimpose a small axisymmetric incremental displacement $\dot{\mathbf{u}} = \dot{u}_r(r, \theta)\mathbf{e}_r + \dot{u}_\theta(r, \theta)\mathbf{e}_\theta$ along with an incremental electric displacement $\dot{\mathbf{D}} = \dot{D}_r(r, \theta)\mathbf{e}_r + \dot{D}_\theta(r, \theta)\mathbf{e}_\theta$ over the radially symmetric solution described in §2. Hereinafter the incremental quantity will be denoted by the notation $(\bullet)$.

In the following, we adopt the convention of summation over repeated indices. The linearized incremental forms of the constitutive relations read [36]

$$\text{and} \quad \left. \begin{aligned} \dot{\mathbf{S}} &= \mathcal{A} : \mathbf{H} + \mathbf{F} \dot{\mathbf{D}} + p\mathbf{H} - \dot{p}\mathbf{I}, & \dot{\mathbf{E}} &= \mathbf{H} : \mathbf{F} + \mathbf{K} \dot{\mathbf{D}} \\ \dot{S}_{ij} &= A_{ij\alpha\beta} H_{\beta\alpha} + \Gamma_{ij\alpha} \dot{D}_\alpha + p H_{ij} - \dot{p} \delta_{ij}, & \dot{E}_i &= H_{\alpha\beta} \Gamma_{\beta\alpha i} + K_{i\alpha} \dot{D}_\alpha, \end{aligned} \right\} \quad (3.1)$$

where $\mathbf{H} = \text{grad } \dot{\mathbf{u}}$ is the displacement gradient, $\mathcal{A}$, $\mathbf{F}$ and $\mathbf{K}$ are, fourth-, third- and second-order electro-elastic moduli tensors, respectively, whose components are given by

$$\left. \begin{aligned} A_{piqj} &= A_{qjpi} = F_{p\alpha} F_{q\beta} \frac{\partial^2 W}{\partial F_{i\alpha} \partial F_{j\beta}}, & \Gamma_{piq} &= \Gamma_{ipq} = F_{p\alpha} F_{\beta q}^{-1} \frac{\partial^2 W}{\partial F_{i\alpha} \partial D_{l\beta}} \\ \text{and} & & K_{ij} &= K_{ji} = F_{\alpha i}^{-1} F_{\beta j}^{-1} \frac{\partial^2 W}{\partial D_{l\alpha} \partial D_{l\beta}}. \end{aligned} \right\} \quad (3.2)$$

The incremental counterpart of the equilibrium equations (2.5)–(2.8) read

$$\text{div } \dot{\mathbf{S}} = \mathbf{0}, \quad (3.3)$$

$$\text{curl } \dot{\mathbf{E}} = \mathbf{0} \quad (3.4)$$

$$\text{and} \quad \text{div } \dot{\mathbf{D}} = 0. \quad (3.5)$$

We introduce an incremental electric potential $\dot{\phi} = \dot{\phi}(r, \theta)$ to rewrite the incremental electric field as $\dot{\mathbf{E}} = -\text{grad } \dot{\phi}$, so that equation (3.4) is automatically satisfied.

For the considered deformation, we have

$$\mathbb{H} = \text{grad } \dot{\mathbf{u}} = \begin{bmatrix} \frac{\partial \dot{u}_r}{\partial r} & \frac{1}{r} \left(\frac{\partial \dot{u}_r}{\partial \theta} - \dot{u}_\theta \right) & 0 \\ \frac{\partial \dot{u}_\theta}{\partial r} & \frac{1}{r} \left(\dot{u}_r + \frac{\partial \dot{u}_\theta}{\partial \theta} \right) & 0 \\ 0 & 0 & \frac{1}{r} (\dot{u}_r + \dot{u}_\theta \cot \theta) \end{bmatrix}. \quad (3.6)$$

The linearized form of the incompressibility constraint (2.3) reads

$$\text{div } \dot{\mathbf{u}} = 0. \quad (3.7)$$

Having assumed that the applied voltage and pressure are fixed and that the two layers are perfectly bonded, the following boundary and interfacial conditions apply

$$\left. \begin{aligned} \dot{S}_{rr}^d &= P \frac{\partial \dot{u}_r}{\partial r}, \quad \dot{S}_{r\theta}^d = \frac{P}{r} \left(\frac{\partial \dot{u}_r}{\partial \theta} - \dot{u}_\theta \right) \quad \text{and} \quad \dot{\phi} = 0 \quad \text{at } r = r_i, \\ \dot{S}_{rr}^d &= \dot{S}_{rr}^e, \quad \dot{S}_{r\theta}^d = \dot{S}_{r\theta}^e \quad \text{and} \quad \dot{\phi} = 0 \quad \text{at } r = r_m, \\ \dot{S}_{rr}^e &= \dot{S}_{rr}^e = 0 \quad \text{at } r = r_o. \end{aligned} \right\} \quad (3.8)$$

and

(b) Stroh formulation

We assume the following separation of variables for the incremental fields [37]

$$\left. \begin{aligned} \{ \dot{u}_r(r, \theta), \dot{S}_{rr}(r, \theta), \dot{\phi}(r, \theta), \dot{D}_r(r, \theta) \} \\ = \{ U_r(r), \Sigma_{rr}(r), \Phi(r), \Delta_r(r) \} P_m(\cos \theta), \\ \{ \dot{u}_\theta(r, \theta), \dot{S}_{r\theta}(r, \theta) \} = \left\{ \frac{U_\theta(r)}{M}, \frac{\Sigma_{r\theta}(r)}{M} \right\} \frac{dP_m(\cos \theta)}{d\theta}, \end{aligned} \right\} \quad (3.9)$$

and

where $M = \sqrt{m(m+1)}$, and P_m indicates the Legendre polynomial of order m , which satisfies the following identity

$$\frac{d^2 P_m(\cos \theta)}{d\theta^2} + \cot \theta \frac{dP_m(\cos \theta)}{d\theta} + M^2 P_m(\cos \theta) = 0. \quad (3.10)$$

Given the Stroh vector $\boldsymbol{\eta}(r) = (U_r, U_\theta, r\Delta_r, r\Sigma_{rr}, r\Sigma_{r\theta}, \Phi)$, the governing equations (3.1), (3.3), (3.5) and (3.7) can be rewritten in the form of a first-order differential system as

$$\frac{d}{dr} \boldsymbol{\eta} = \frac{1}{r} \mathbb{G} \boldsymbol{\eta} = \frac{1}{r} \begin{bmatrix} \mathbb{G}_1 & \mathbb{G}_2 \\ \mathbb{G}_3 & \mathbb{G}_4 \end{bmatrix} \boldsymbol{\eta}, \quad (3.11)$$

where the matrix $\mathbb{G} \in \mathbb{R}^{6 \times 6}$ is the so-called Stroh matrix. The derivation of equation (3.11) and the components of the 3×3 sub-matrices $\mathbb{G}_1, \mathbb{G}_2, \mathbb{G}_3$ and $\mathbb{G}_4$ are detailed in the electronic supplementary material.

We introduce the generalized displacement and traction vectors, defined as $\mathbf{U} = (U_r, U_\theta, r\Delta_r)$ and $\mathbf{S} = (r\Sigma_{rr}, r\Sigma_{r\theta}, \Phi)$, respectively. Then, using equation (3.9), the incremental boundary conditions (3.8)_{1,3} can be rewritten as

$$\mathbf{S}^d(r_i) = P \begin{bmatrix} -2 & M & 0 \\ M & -1 & 0 \\ 0 & 0 & 0 \end{bmatrix} \mathbf{U}^d(r_i) \quad \text{and} \quad \mathbf{S}^e(r_o) = \mathbf{0}, \quad (3.12)$$

and the incremental interfacial condition (3.8)₂ can be rewritten as

$$\mathbf{S}^d(r_m) = \mathbf{S}^e(r_m) \quad \text{and} \quad \mathbf{U}^d(r_m) = \mathbf{U}^e(r_m). \quad (3.13)$$

(c) The surface impedance matrix method

Here we exploit the so-called surface impedance matrix method to build a robust numerical procedure to solve the governing equation (3.11) associated with the incremental boundary condition (3.12) and interfacial condition (3.13).

For each layer, we introduce the conditional impedance matrices $Z^d(r, r_i)$ and $Z^e(r, r_o)$ [38]. In particular, we have

$$S^s = Z^s U^s \quad (s = d, e). \quad (3.14)$$

Then we can expand equation (3.11) to obtain (with s omitted)

$$\frac{d}{dr} U = \frac{1}{r} G_1 U + \frac{1}{r} G_2 Z U \quad \text{and} \quad \frac{d}{dr} (Z U) = \frac{1}{r} G_3 U + \frac{1}{r} G_4 Z U. \quad (3.15)$$

Elimination of U in equation (3.15) gives the following Riccati differential equation for Z

$$\frac{dZ}{dr} = \frac{1}{r} (-ZG_1 - ZG_2Z + G_3 + G_4Z). \quad (3.16)$$

From the incremental boundary condition (3.12), we have

$$Z^d(r_i, r_i) = P \begin{bmatrix} -2 & M & 0 \\ M & -1 & 0 \\ 0 & 0 & 0 \end{bmatrix} \quad \text{and} \quad Z^e(r_o, r_o) = 0. \quad (3.17)$$

The marginal stability curves for the layered balloon can be determined as follows. First, we determine the deformation and material constants for a given voltage V and a given inner pressure P , based on the results presented in §2. Then, we integrate equation (3.16) in the DE layer from r_i to r_m , in order to obtain $Z^d(r_m, r_i)$, with the initial condition (3.17)₁. In the elastic layer, we integrate equation (3.16) from r_o to r_m to obtain $Z^e(r_m, r_o)$, with the initial condition (3.17)₂. We finally iterate on the stretch until the following bifurcation criterion is satisfied

$$\det[Z^e(r_m, r_o) - Z^d(r_m, r_i)] = 0. \quad (3.18)$$

For the considered problem, the critical inner stretch for the onset of a mechanical instability can be solved from the dispersion equation (3.18), which is a function of the applied voltage, the pressure, the mode m , and the material and structural parameters of the balloon, such that:

$$\lambda_i^c = \lambda_i^c(V, P, m; \mu^d, \mu^e, \varepsilon, t^d, t^e). \quad (3.19)$$

4. Marginal stability curves for Gent dielectric-elastomer balloons

(a) Constitutive equations

In order to illustrate the results of the linear stability analysis, we adopt the following ideal *Gent dielectric model* [10] and the *Gent elastic model* [39] to describe the DE and elastic elastomers, respectively,

$$\left. \begin{aligned} W^d(F, D_R) &= -\frac{\mu^d G^d}{2} \ln \left(1 - \frac{I_1 - 3}{G^d} \right) + \frac{I_5}{2\varepsilon} \\ \text{and} \quad W^e(F) &= -\frac{\mu^e G^e}{2} \ln \left(1 - \frac{I_1 - 3}{G^e} \right), \end{aligned} \right\} \quad (4.1)$$

where μ^s and G^s are the shear modulus and the dimensionless stiffening parameter of the s th ($s = d, e$) elastomer, respectively, ε is the strain independent permittivity of the DE elastomer. These constitutive laws model the strain stiffening behaviour of soft polymers. In the following, we fix $G^d = G^e = 97.2$, an experimental parameter collected for unfilled vulcanized rubber [24,39]. Note that in the limit of $G^s \rightarrow \infty$, the Gent model reduces to the neo-Hookean model [40,41].

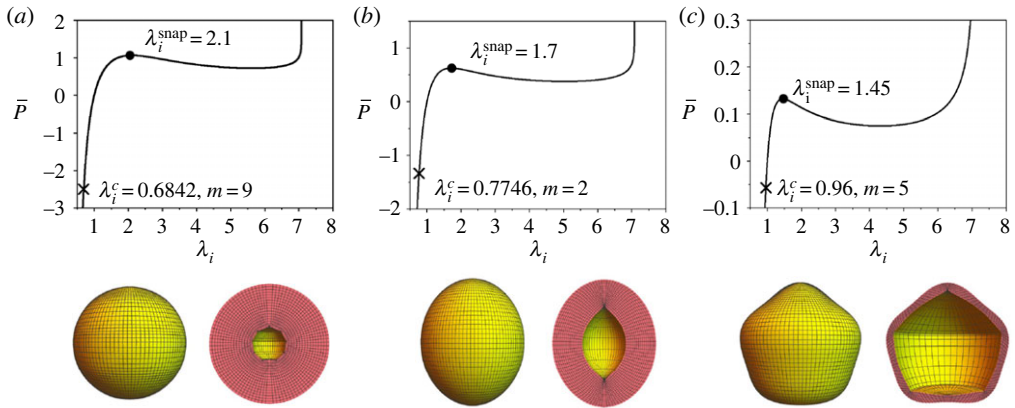


Figure 3. Inflation and buckling responses of (a) thick, (b) moderately thick and (c) thin elastic balloons ($\bar{V} = 0$, $t^d = 1$), respectively. The cross and circle markers indicate the thresholds for buckling in compression and snap-through instabilities of the material, respectively. The upper row presents the $\bar{P} - \lambda_i$ curve, and the lower row shows the shape of the balloon at the onset of buckling. Note that we have set a finite amplitude of the incremental displacement for the sake of graphical illustration of the buckling pattern. (a) $t^e = 0.4$, (b) $t^e = 0.6$ and (c) $t^e = 0.9$.

(b) Marginal stability curves

We now derive the marginal stability curves to investigate the influence of the presence of the elastic inactive layer on the deformation and instabilities of the DE active balloon, and explore the possibility of realizing the selection of specific instability mode in layered DE devices through structural and material design. For this purpose, we compare the nonlinear responses, as well as the onsets of the snap-through and the buckling instabilities of a monolayer elastic balloon, a monolayer DE balloon and a layered dielectric-elastic balloon.

For convenience and generality, we introduce the following dimensionless quantities,

$$\left. \begin{aligned} \bar{P} &= \frac{P}{\mu^d} \quad \text{and} \quad \bar{T}_{ii}^s = \frac{T_{ii}^s}{\mu^d} \quad (s = d, e) \\ \text{and} \quad \bar{V} &= \frac{V}{R_m - R_i} \sqrt{\frac{\varepsilon}{\mu^d}} \quad \text{and} \quad \bar{D}_R = \frac{D_R}{\sqrt{\mu^d \varepsilon}} \end{aligned} \right\} \quad (4.2)$$

(i) Results for a monolayer elastic balloon

We first consider the case of an elastic balloon ($\bar{V} = 0$, $t^d = 1$) subject to an internal pressure $\bar{P}$, whose results are depicted in figure 3. We can see that the $\bar{P} - \lambda_i$ curve of the balloon is clearly non-monotonic and the snap-through behaviour can be observed at the critical stretches highlighted by the round markers. The stretch λ_i first increases as the pressure $\bar{P}$ (> 0) increases. Once the pressure reaches a critical value, the stretch increases suddenly and the pressure inside the balloon decreases due to the dramatic increase of the volume. Due to the strain-stiffening effect of the material, the internal pressure increases again as the stretch approaches the extensible limit of the material. The snap-through enables a large strain change in the balloon, which is a desired actuation mechanism in many engineering applications. It is noted that the critical internal pressure for triggering the snap-through instability of a thin balloon is smaller than that of a thick balloon.

On the other hand, buckling may occur in an elastic balloon subject to critical compression ($\bar{P} < 0$). Compared with a thick-walled balloon, a balloon with a smaller thickness is more susceptible to buckling. We note that the critical mode m (i.e. the first mode to become unstable as the pressure decreases) can be selected by properly designing the thickness of the balloon. Typically, the outer contour of a buckled thick-walled balloon maintains the spherical

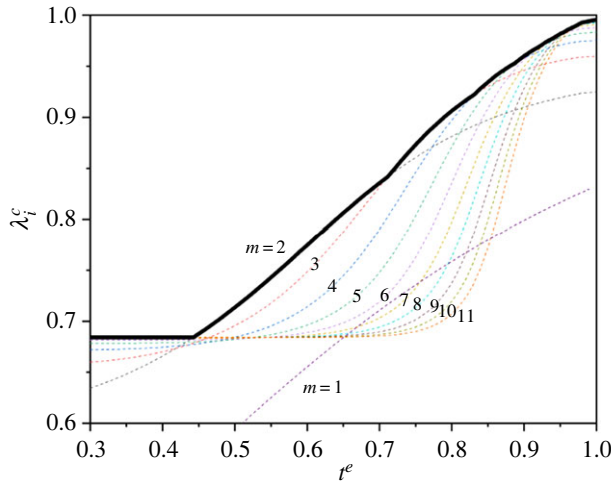


Figure 4. Plots of the critical strains of a Gent elastic balloon as functions of the radius ratio t^e , shown at different buckling modes $m = 1, 2, \dots, 11$ (dashed lines). The bold black line corresponds to the marginal stability curve.

configuration and wrinkles appear on the inner face (figure 3*a*). While for a thin-walled balloon, buckling affects the whole body (figure 3*b,c*).

In figure 4, we plot the critical stretch versus the aspect ratio t^e at different buckling modes, computed from the dispersion equation (3.18). Buckling occurs once the stretch reaches the marginal stability threshold, i.e. the bold black curve in the figure. We note that the buckling mode $m = 1$ is not allowed independently of the thickness of the balloon. The buckling mode $m = 2$ can occur in moderately thick balloons ($0.45 < t^e < 0.7$), while for thick balloons ($t^e \leq 0.45$) and thin balloons ($t^e \geq 0.75$), higher mode ($m > 2$) are selected, strongly depending on the aspect ratio. We remark that for thick balloons with $t^e \leq 0.45$, buckling always occurs once the inner circumferential stretch reaches $\lambda_i^c = 0.684$, which is thickness independent.

We emphasize that a critical compression ($\bar{P} < 0$) is required for a Gent elastic balloon to trigger the onset of buckling, which is different from the DE case presented below.

(ii) Results for a monolayer DE balloon

Here, we consider a thin DE balloon ($t^e = 1, t^d = 0.9$) subject to a combination of an internal pressure $\bar{P}$ and a voltage $\bar{V}$, whose results are collected in figure 5. In order to investigate the effect of the applied voltage on the onset of buckling, we consider the cases of $\bar{V} = 0.1$ and $\bar{V} = 0.3$ as illustrative examples.

For a DE balloon subject to a small voltage ($\bar{V} = 0.1$), the response is similar to the case of a purely elastic monolayer presented in figure 3. The balloon buckles only when a critical compression ($\bar{P} < 0$) is applied. On the other hand, the snap-through instability is triggered once a critical inner pressure $\bar{P} (> 0)$ is applied, and the balloon survives the snap-through instability, without encountering the buckling failure.

When the applied voltage is sufficiently large ($\bar{V} = 0.3$), we see that in addition to buckling in compression, the possibility of a bifurcation in extension ($\bar{P} > 0$) emerges along the path of the snap-through. In this case, the balloon cannot reach a homogeneous state characterized by a large strain.

We plot in figure 6, the critical stretch λ_i^c versus t^d for monolayer DE balloons subject to either $\bar{V} = 0.1$ or $\bar{V} = 0.3$. Here we use the notation λ_i^V to denote the inner circumferential stretch of the balloon induced by the applied voltage only, i.e. considering $\bar{P} = 0$.

For the case $\bar{V} = 0.1$, the balloon expands radially to $\lambda_i^V = 1.014$, until buckling occurs at a critical compression. The snap-through instability of the elastomer will be triggered at a critical

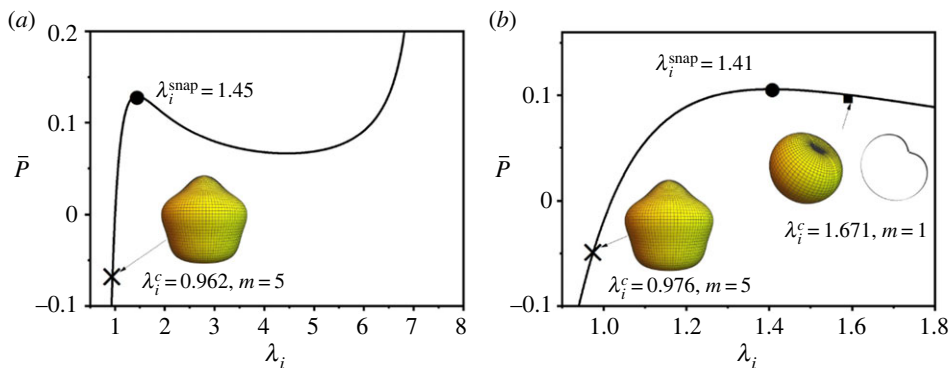


Figure 5. Inflation and buckling responses of thin DE balloons ($t^e = 1$, $t^d = 0.9$) subject to a fixed voltage: (a) $\bar{V} = 0.1$ and (b) $\bar{V} = 0.3$. The cross, circle and square markers indicate the thresholds for buckling in compression, snap-through and buckling in extension instabilities of the material, respectively. Inset: the shape of the balloon at the onset of buckling; and the sectional view of the balloon at necking.

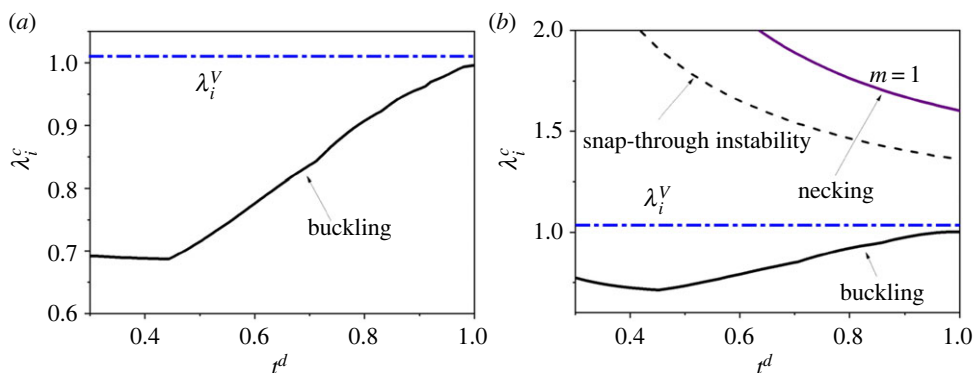


Figure 6. Plots of the critical strains versus the radius ratio t^d for a single layer of DE ($t^e = 1$): (a) $\bar{V} = 0.1$ and (b) $\bar{V} = 0.3$. The black dashed line depicts the snap-through instability threshold, the blue dot-dashed line depicts the inner circumferential stretch λ_i^V of the balloon induced by the applied voltage only, i.e. considering $\bar{P} = 0$. The magenta solid line finally depicts the threshold for necking. For simplification, here we do not show the instability thresholds for the different modes $m = 1, 2, \dots, 11$ (dashed lines as in figure 4), but only present the actual marginal stability curve.

inner pressure $\bar{P} > 0$ (see figure 5 (left) for the special case $t^d = 0.9$). We note that no bifurcation occurs during the snap-through process, thus the balloon can achieve a large actuation strain (in figure 6 (left) the snap-through curve is not presented).

For the case $\bar{V} = 0.3$, in addition to the buckling in compression, a bifurcation in tension also occurs. The snap-through occurs prior to the bifurcation, thus snap-through cannot be exploited to obtain a large actuation strain, since the balloon would lose its spherical configuration during the snap-through process. As shown in figure 5 (right), the critical mode for the bifurcation in tension is $m = 1$, and a localized thinning of the DE occurs, which is the typical feature of necking instability [32,33]. It is noted that we can design the buckling mode in compression by properly selecting the thickness of the balloon, while $m = 1$ is always the critical mode in tension.

We conclude that due to the electro-mechanical coupling effect, the DE balloon may undergo snap-through-induced necking, thus limiting its applicability as an actuating device.

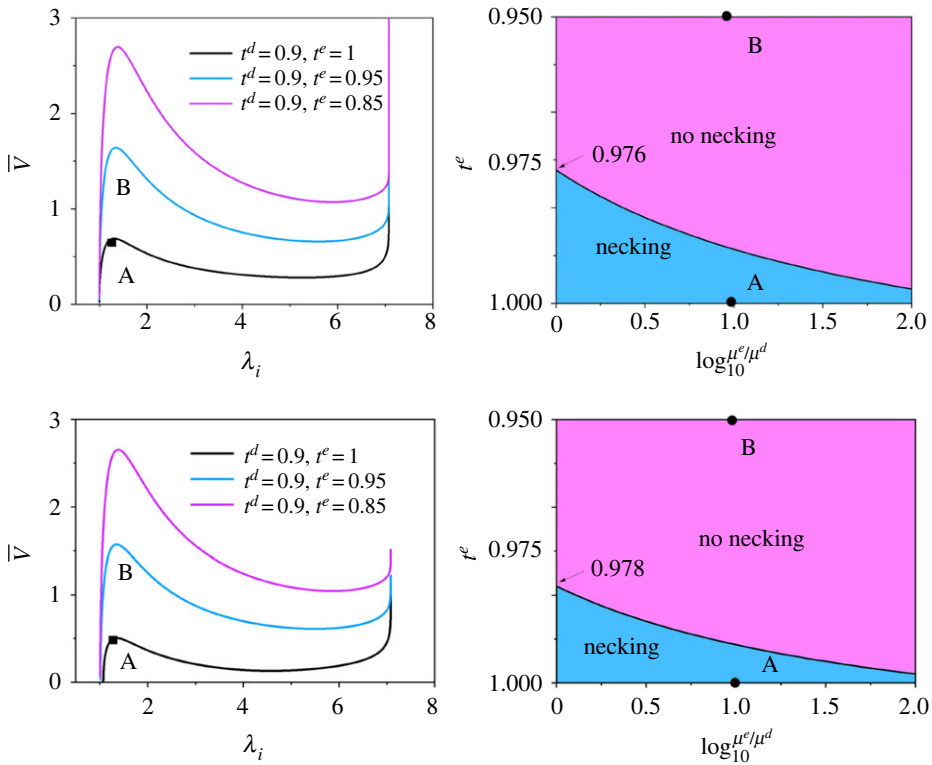


Figure 7. Inflation of voltage-activated ($\bar{P} = 0$ top, $\bar{P} = 0.06$ bottom) dielectric-elastic balloons with $t^d = 0.9$ and varying t^e . Left: $\bar{V} - \lambda_i$ curve of the balloon at fixed $\mu^e / \mu^d = 10$ and varying t^e , with the square marker indicating the necking threshold. Right: stability diagram of the balloons with varying t^e and $\log_{10} \mu^e / \mu^d$. The black, blue and red curves on the left column correspond to three specific balloons: balloon A with $t^d = 0.9, t^e = 1$, balloon B with $t^d = 0.9, t^e = 0.95$, and balloon C with $t^d = 0.9, t^e = 0.85$ (balloon C beyond the scope of the phase diagram thus is not presented in the plots on the right).

(iii) Results for a bi-layered dielectric-elastic balloon

Finally, we investigate the case of a bi-layered dielectric-elastic balloon, as both voltage and pressure tuning methods are considered.

In figure 7 (left), we show the voltage-stretch curves and the necking thresholds of electroactive bi-layered balloons ($\bar{P} = 0$ and 0.06) with $t^d = 0.9$ and varying t^e, μ^d and μ^e . We consider the balloons with fixed material parameter $\mu^e / \mu^d = 10$. The results for a monolayer DE balloon are presented here for comparison. We remark that the snap-through instability always exists in bi-layered balloons, which is independent of the thickness of the elastic layer. Compared with balloons with a thin elastic layer, a larger voltage is required to activate the snap-through instability in balloons with a thick elastic layer, increasing the risk of electric breakdown failure. It is worth noting that for dielectric-elastic balloons with a thin elastic layer (here $t^e = 1$ for example), a bifurcation in tension (i.e. necking instability) occurs after the snap-through instability is triggered, although the thresholds of the critical stretches for the two mechanical instabilities are very close. As expected, covering the DE balloon with an elastic layer with specific thickness (here $t^e = 0.95, 0.85$, for example) can suppress the bifurcation in tension. As a result, the structure can survive the snap-through procedure and achieve large deformation without necking, thus being suitable for engineering applications as an actuator. We also note that as the pressure increases, the critical voltage required to trigger the snap-through instability decreases.

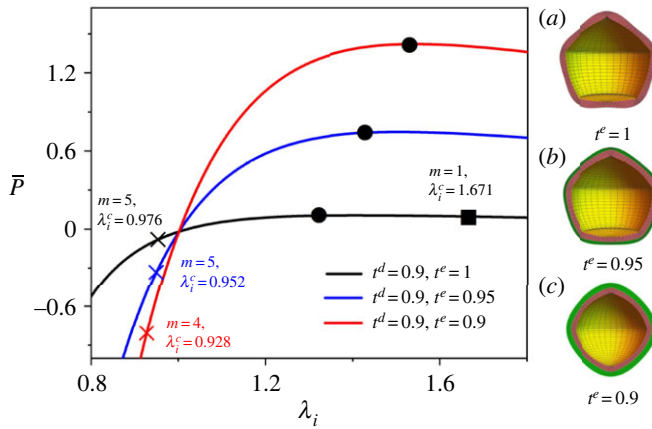


Figure 8. Inflation and buckling responses of pressure activated ($\bar{V} = 0.3$) dielectric-elastic balloons with $t^d = 0.9$ and varying t^e . The $\bar{P} - \lambda_i$ curve is shown on the left, and the buckling shapes are shown on the right (a–c). The cross, circle and square markers indicate the thresholds for buckling in compression, snap-through and buckling in extension, respectively.

In order to study the influence of the thickness of the elastic layer on the necking instability of the bi-layered balloon, we plot the $t^e - \log_{10}^{\mu^e/\mu^d}$ phase diagram on figure 7 (right). For $\bar{P} = 0$, we can see that the necking may occur when the thickness of the elastic layer is small. As the thickness of the elastic layer increases (e.g. $t^e < 0.976$ for balloons with $\mu^d = \mu^e$), the necking of the balloon can be suppressed. As the internal pressure or the stiffness of the elastic layer ($\mu^e = 10\mu^d$ for example) increase, we note a decrease in the critical thickness of the elastic layer required to suppress the necking instability.

Figure 8 presents the inflation-stretch curves bi-layered balloons ($\bar{V} = 0.3$) with $t^d = 0.9$, $\mu^e/\mu^d = 10$ and varying t^e . We remark that for the case of a monolayer DE layer ($t^e = 1$), both buckling and necking can be induced by properly tuning the pressure $\bar{P}$. The presence of the elastic layer can not only decrease the risk of buckling but can also suppress the necking of the balloon. The selection of buckling pattern of the balloons can be designed by setting the thickness of the elastic layer.

We conclude that for a monolayer DE balloon, the tensile necking may be triggered during the snap-through process, limiting the actuation strain. The application of the elastic layer outside the DE layer can enhance the snap-through instability to avoid a bifurcation in tension, thus can dramatically increase the actuation strain of the balloon. That is, a monolayer DE balloon is more suitable for making functional devices with complex surface morphology, while a bi-layered dielectric-elastic balloon is more suitable as an actuating device as stable large deformation can be achieved.

5. Fully nonlinear numerical simulations

In this section, we first implement a numerical scheme to approximate the nonlinear BVP given by equations (2.3)–(2.15). Second, we perform the numerical simulations, discussing the morphological transitions in the fully nonlinear regime in some cases of practical interest.

(a) Variational formulation

We take the displacement field $\mathbf{u}$ and the electric potential field ϕ as the unknowns of the problem. We assume radial symmetry of the solutions performing numerical simulations of an axis-symmetric section of the balloon, namely on $\mathcal{S}_0 = \mathcal{B}_0 \cap (X_3 = 0 \text{ and } X_1 > 0)$.

For the sake of numerical robustness, we use a quasi-incompressible approximation. The BVP given by equations (2.3)–(2.15) rewrites

$$\left\{ \begin{array}{ll} \mathbb{S} = \frac{\partial W^*}{\partial \mathbb{F}}, & \mathbf{D}_L = -\frac{\partial W^*}{\partial \mathbf{E}_L}, \\ \text{Div } \mathbb{S} = \mathbf{0} & \text{in } S_0 \\ \text{Div } \mathbf{D}_L = \mathbf{0} & \text{in } S_0^d \\ \mathbb{S}^T \mathbf{N} = -P \mathbb{F}^{-T} \mathbf{N}, \quad \phi = 0 & \text{if } R = R_i \\ \mathbb{S}^T \mathbf{N} = \mathbf{0} & \text{if } R = R_o \\ \phi = V & \text{if } R \geq R_m \\ \mathbf{u} \cdot \mathbf{e}_1 = 0, \quad \mathbf{e}_2 \cdot \mathbb{S}^T \mathbf{e}_1 = 0 & \text{if } X_1 = 0 \\ \int_{S_0} X_1 \mathbf{u} \cdot \mathbf{e}_2 \, dX_1 \, dX_2 = 0 \end{array} \right. \quad (5.1)$$

where $(\mathbf{e}_1, \mathbf{e}_2, \mathbf{e}_3)$ is the canonical vector basis in Cartesian coordinate. The last equation in (5.1) removes rigid body translations along the vertical direction $\mathbf{e}_2$, while the energy density $W^*(\mathbb{F}, \mathbf{E}_L)$ is linked to $W(\mathbb{F}, \mathbf{D}_L)$ through the following Legendre transform

$$W(\mathbb{F}, \mathbf{D}_L) = W^*(\mathbb{F}, \mathbf{E}_L) + \mathbf{D}_L \cdot \mathbf{E}_L. \quad (5.2)$$

The BVP given by equations (2.3)–(2.15) can be cast into an equivalent variational formulation. The integral condition in (5.1) is enforced by means of a Lagrange multiplier α .

Let us introduce the energy functional

$$\mathcal{E}[\mathbf{u}, \phi, \alpha] = 2\pi \int_{S_0} X_1 [W^*(\mathbb{F}, \mathbf{E}_L) + \alpha \mathbf{u} \cdot \mathbf{e}_2] \, dX_1 \, dX_2. \quad (5.3)$$

Then, the solutions of the BVP (2.3)–(2.15) must satisfy [42]

$$\delta \mathcal{E}(\mathbf{u}, \phi, \alpha) [\delta \mathbf{u}, \delta \phi, \delta \alpha] + 2\pi \int_{R=R_i} J X_1 P \mathbb{F}^{-1} \delta \mathbf{u} \cdot \mathbf{N} \, dS = 0, \quad (5.4)$$

where $J = \det \mathbb{F}$, $\delta \mathcal{E}$ is the first variation of the energy functional $\mathcal{E}$ and $\delta \mathbf{u}, \delta \phi, \delta \alpha$ are admissible variations of the unknown fields.

As a compressible counterpart of equation (4.1), we take the energy densities for the DE and the passive elastomer as follows

$$\left. \begin{array}{l} W^{*d}(\mathbb{F}, \mathbf{E}_L) = -\frac{\mu^d G^d}{2} \log \left(1 - \frac{\bar{I}_1 - 3}{G^d} \right) + \frac{K^d}{2} (\log J)^2 - \frac{\varepsilon J}{2} \mathbf{E}_L \cdot \mathbf{C}^{-1} \mathbf{E}_L \\ \text{and} \quad W^{*e}(\mathbb{F}) = -\frac{\mu^e G^e}{2} \log \left(1 - \frac{\bar{I}_1 - 3}{G^e} \right) + \frac{K^e}{2} (\log J)^2, \end{array} \right\} \quad (5.5)$$

where K^d and K^e are parameters regulating the compressibility of each layer and $\bar{I}_1 = J^{-2/3} I_1$.

(b) Mixed finite-element implementation

The problem is approximated by means of the finite element method. The computational domain S_0 is discretized by using a triangular mesh. In order to impose homogeneous boundary conditions on the potential field, we decompose the potential ϕ into two contributions

$$\phi(\mathbf{X}) = \phi_r(\mathbf{X}) + \phi_{\text{inh}}(\mathbf{X}), \quad (5.6)$$

where $\phi_r(\mathbf{X}) = V(R - R_i)/(R_m - R_i)$ if $R \leq R_m$, while $\phi_r(\mathbf{X}) = V$ if $R > R_m$. Thus, the unknowns of the problem are $\mathbf{u}$, ϕ_{inh} and the Lagrange multiplier α . The fields $\mathbf{u}$ and ϕ_{inh} are approximated by means of a mixed finite-element formulation, using continuous piecewise quadratic functions for the displacement field and continuous piecewise linear functions for ϕ_{inh} . In order to trigger

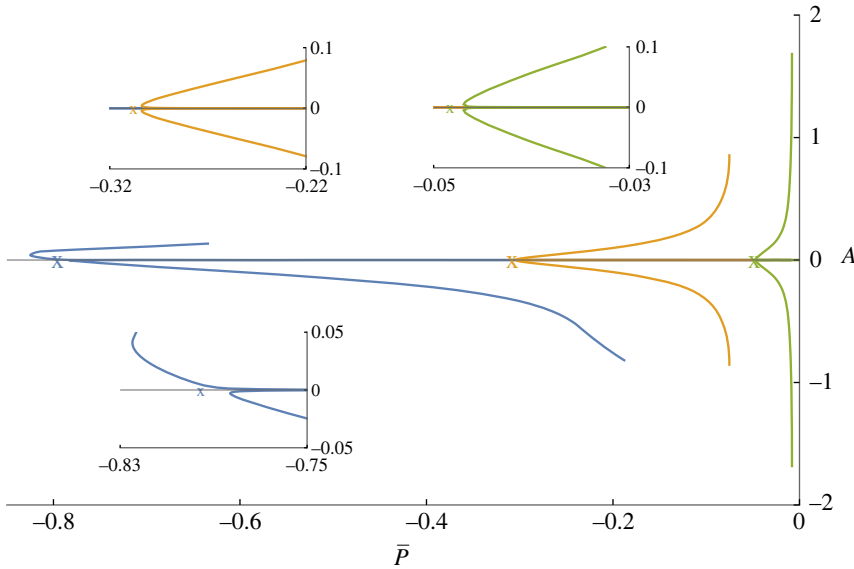


Figure 9. Post-buckling behaviour showing $\bar{P}$ versus the dimensionless amplitude of the deformation at the free surface, setting $\bar{V} = 0.3$, $\mu^e/\mu^d = 10$, $t^d = 0.9$ and $t^e = 0.9, 0.95, 1$ (blue, orange and green lines, respectively). The cross marker denotes the theoretical buckling threshold.

the bifurcation, we apply a small perturbation to the mesh. The expression of the perturbation is given by the critical mode provided by the results of the linear stability analysis [43].

The numerical scheme is implemented in Python by using the open-source computing platform FEniCS, v. 2019.2 [44]. We use PETSc as a linear algebra back-end. In order to reconstruct the bifurcation diagram, we use a pseudo-arclength continuation algorithm [45], where we use the pressure P as a control parameter of the problem. The nonlinear problem is solved by using a predictor–corrector method. In particular, we adopt a secant predictor to obtain a first guess of the solution and a SNES Newton solver as a corrector. The variational formulation, as well as the Jacobian of the linearized problem, are computed by means of the library UFL [46]. We exploit the library BiFEniCS (<https://github.com/riccobelli/bifenics>) for the implementation of the continuation algorithm [47].

(c) Results of the numerical simulations

In the following, we show the results of simulations for the cases analysed in figure 8. Specifically, we take $t^d = 0.9$ and $t^e = 0.9, 0.95, 1$ (the latter case corresponds to a single DE layer), with $\mu^e/\mu^d = 10$ and $\bar{V} = 0.3$.

We apply a perturbation of amplitude $\delta A = \pm 10^{-5} R_0$. In figure 9, we show the bifurcation diagram for $\bar{P} < 0$. As a measure of the amplitude of the bifurcated pattern, we use the following scalar dimensionless quantity

$$A = \pm \frac{1}{R_0} \left(\max_{|X|=R_0} |\mathbf{u}| - \min_{|X|=R_0} |\mathbf{u}| \right), \quad (5.7)$$

where we take a plus or a minus in front of the amplitude depending on the sign of δA .

In the cases $t^e = 0.95, 1$, the buckling mode is $m = 5$, which is symmetric with respect to the substitution $\delta A \rightarrow -\delta A$. As expected, the bifurcation diagram for this case is symmetric with respect to the $\bar{P}$ -axis. In both cases, the shape of the bifurcation is a subcritical pitchfork. Conversely, for $t^e = 0.9$ the buckling mode is even. In such a case, the buckling mode is not symmetric with respect to the substitution $\delta A \rightarrow -\delta A$. As depicted in figure 9,

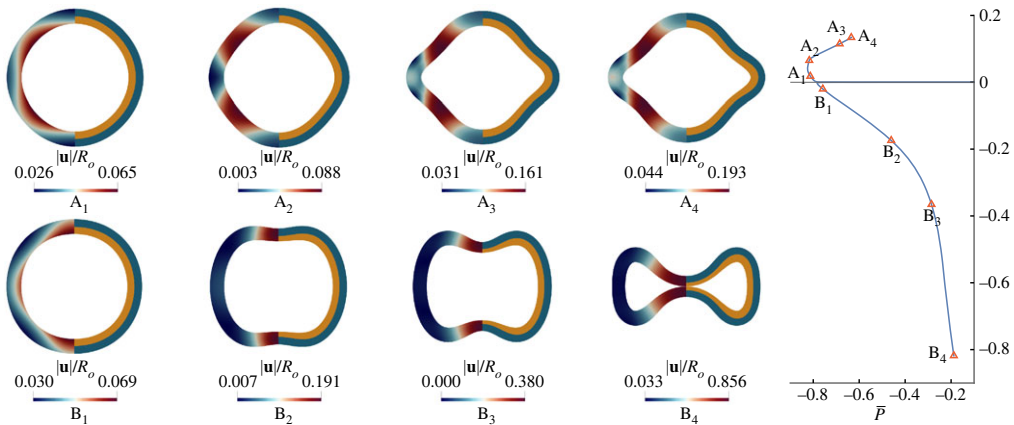


Figure 10. (left) Plot of the actual configuration of the planar section of spherical bilayers, with $t^d = 0.9$, $t^e = 0.9$, $\mu^e/\mu^d = 10$. Here, we show a section of the shell, where on the left we show $\|u\|/R_o$, while on the right each layer is identified using different colours (orange: DE, blue: elastomer). On the right, we show the corresponding points to each configuration on the bifurcation diagram.

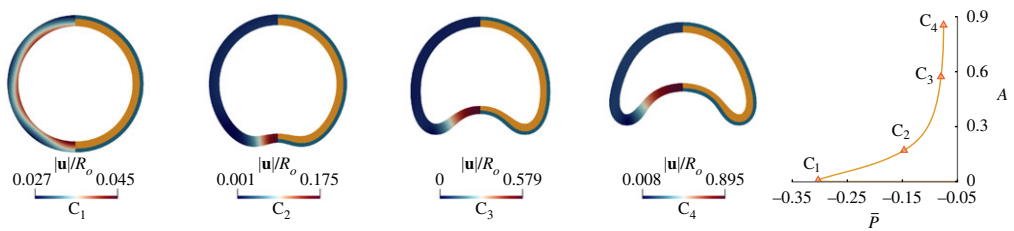


Figure 11. (left) Plot of the actual configuration of the planar section of spherical bilayers, with $t^d = 0.9$, $t^e = 0.95$, $\mu^e/\mu^d = 10$, $\bar{V} = 0.3$. Here, we show a section of the shell, where on the left we show $\|u\|/R_o$, while on the right each layer is identified using different colours (orange: DE, blue: elastomer). On the right, we show the corresponding points to each configuration on the bifurcation diagram.

the bifurcation related to this case becomes transcritical. In all the cases, the numerical outcomes are in good agreement with the theoretical buckling thresholds, as shown in figure 9.

In figures 10 and 11, we show the evolution of the buckled configurations for the bi-layered balloon. In particular, in the case where $t^e = 0.9$ we have two possible buckled configurations: in the former we observe the formation of a protrusion along the equatorial line; while in the latter the two poles collapse until we reach the self-contacting configuration of the shell. Instead, if $t^e = 0.95$, the bifurcation diagram is symmetric, and only one branch will be shown. We observe that the formation of a dimple is close to one of the poles. The initial amplitude of such a dimple is dictated by the critical buckling mode.

In extension, only the DE balloon ($t^e = 1$) undergoes necking. As shown in figure 12, the bifurcation is symmetric with respect to the $\bar{P}$ -axis, exhibiting a pitchfork bifurcation at a stretch that is higher than the snap-through threshold, see figure 7. Therefore, $\bar{P}$ first increases beyond the necking threshold, then decreases before undergoing necking. In figure 13, we show the actual configuration of the DE balloon. We observe a progressive thinning of the dielectric elastomer, which is a sign of criticality since it is regarded as a precursor of the DE failure [34].

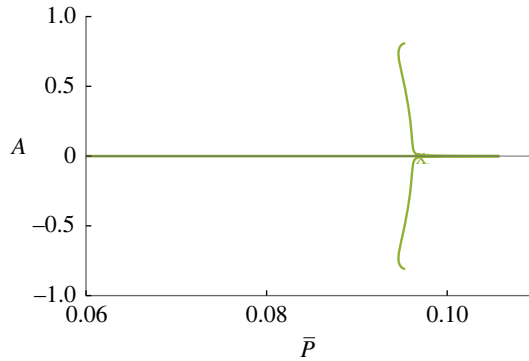


Figure 12. Bifurcation diagram showing $\bar{P}$ versus the dimensionless amplitude of the deformation on the free surface A for $\bar{V} = 0.3$, $\mu^e/\mu^d = 10$, $t^d = 0.9$, and $t^e = 1$, $\bar{V} = 0.3$. The marker cross denotes the theoretical buckling threshold.

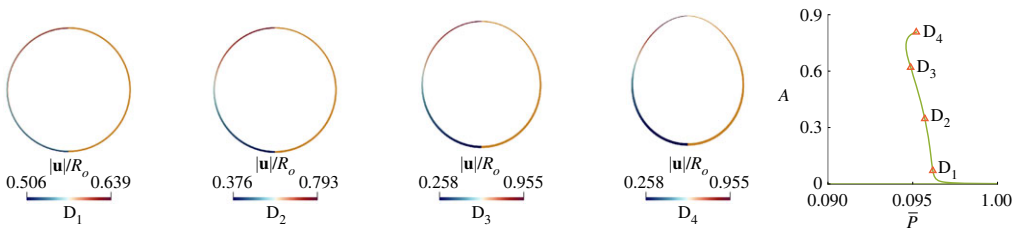


Figure 13. (left) Plot of the actual configuration of DE balloons, with $t^d = 0.9$, $\mu^e/\mu^d = 10$, $\bar{V} = 0.3$. Here, we show a planar section of the balloon, where on the left we show $||u||/R_o$, while on the right each layer is identified using different colours (orange: DE, blue: elastomer). On the right, we show the corresponding points to each configuration on the bifurcation diagram.

6. Conclusion

DEs are promising electro-mechanical materials, especially suitable for applications as soft actuators and functional wearable devices. The mathematical analysis of layered DE balloons is of considerable complexity, due to many theoretical and numerical challenges given by the geometric and material nonlinearities, as well as the electro-mechanical coupling. In this paper, we have proposed a theoretical framework for the analysis of the nonlinear response and the bifurcation diagram of layered dielectric-elastic balloons, reporting complex morphological transitions due to the interplay of snap-through, buckling and necking instabilities. After performing a linear stability analysis based on incremental methods in nonlinear elasticity, we have implemented a numerical algorithm using an original mixed finite-element approach coupled with a pseudo-arclength continuation method to investigate the shape transitions of the balloon in the fully nonlinear regime. The onset of the bifurcated branches in the numerical simulations are in excellent agreement with the theoretical marginal stability thresholds.

In the nonlinear regime, we found that axisymmetric odd modes result into pitchfork bifurcations for balloons subject to negative inner pressure, while even modes are associated with transcritical bifurcations, as shown in figure 9. Not surprisingly, the two branches associated with such transcritical bifurcation exhibit very different behaviours, leading to distinct morphologies, see figure 10. Conversely, if the shell is inflated we observe necking, where the critical mode is always equal to one. The finite-element simulations show a progressive thinning of the DE in the nonlinear regime. This is regarded in the literature as a precursor of failure of the DE [34]. Such a transition takes place in the unstable region of the snap-through instability, see figure 13.

In summary, we have shown that during the snap-through process, a mono-layered DE balloon may be subject to necking, which limits its applications. A layered dielectric-elastic balloon allows to overcome this drawback. Our numerical results also demonstrated that the presence of the elastic layer outside the DE layer has a stabilizing effect on the contractile buckling, and can suppress the necking induced by the snap-through instability of the balloon.

In this work, we adopted some simplifications that deserve a final discussion. For example, the DE and elastic layers of the balloon are taken to be perfectly bonded. While imperfections may exist in layered structures due to manufacturing problems. However, they have been found of negligible influence on the mechanical response of the structures [48]. In addition, we did not take into account the influences of viscoelasticity [49] and electric breakdown failure [50], which have been experimentally observed in DEs, and that will be the focus of future studies. As regards the nonlinear finite-element analysis, other non-axisymmetric modes could also occur. Future efforts will be devoted to the extension of the proposed numerical scheme to three-dimensional simulations. Furthermore, it would also be interesting to compare our theoretical results with some experiments on spherical DE balloons.

Despite making specific constitutive assumptions for illustrative purposes, the findings in this paper can be generally applied to give new paradigms for the design and fabrication of functional DE devices. Indeed, we have shown that the presence of an elastic layer can modulate the response of the DE. By tuning the stiffness and the thickness of the elastic layer, we have shown how either to select the balloon morphological transition or to delay (or even inhibit) the DE necking.

Data accessibility. The source code is available from the GitHub repository: https://github.com/riccobelli/dielectric_elastomer_balloon.

Details on the derivation of the Stroh formulation are provided in the electronic supplementary material [51].

Authors' contributions. Y.S.: conceptualization, formal analysis, investigation, methodology, validation, visualization, writing—original draft, writing—review and editing; D.R.: formal analysis, investigation, methodology, software, validation, visualization, writing—original draft, writing—review and editing; Y.C.: formal analysis, investigation, methodology, validation, visualization, writing—review and editing; W.C.: formal analysis, supervision, writing—review and editing; P.C.: conceptualization, funding acquisition, methodology, supervision, writing—original draft, writing—review and editing.

All authors gave final approval for publication and agreed to be held accountable for the work performed therein.

Conflict of interest declaration. We declare we have no competing interests.

Funding. Y.S., D.R. and P.C. have been partially supported by MUR, PRIN Research Projects 2020F3NCPX and grant Dipartimento di Eccellenza 2023-2027, D.R. has been partially supported by the National Institute of Higher Mathematics through the grant 'INdAM—GNFM Project', code CUP_E53C22001930001. Partial support from the Shenzhen Scientific and Technological Fund for R&D, People's Republic of China (grant no. 2021Szvup152) and the National Natural Science Foundation of China (grant nos. 12192210 and 12192211) to W.C. are also acknowledged.

Acknowledgements. Y.S., D.R. and P.C. are members of the Gruppo Nazionale di Fisica Matematica—INdAM.

References

1. Kim KJ, Tadokoro S. 2007 Electroactive polymers for robotic applications. *Artif. Muscles Sens.* **23**, 291. (doi:10.1007/978-1-84628-372-7)
2. O'Halloran A, O'malley F, McHugh P. 2008 A review on dielectric elastomer actuators, technology, applications, and challenges. *J. Appl. Phys.* **104**, 9. (doi:10.1063/1.2981642)
3. Suo Z, Zhao X, Greene WH. 2008 A nonlinear field theory of deformable dielectrics. *J. Mech. Phys. Solids* **56**, 467–486. (doi:10.1016/j.jmps.2007.05.021)
4. Su Y, Chen W, Destrade M. 2019 Tuning the pull-in instability of soft dielectric elastomers through loading protocols. *Int. J. Non-Linear Mech.* **113**, 62–66. (doi:10.1016/j.ijnonlinmec.2019.03.008)

5. Huang J, Shian S, Suo Z, Clarke DR. 2013 Maximizing the energy density of dielectric elastomer generators using equi-biaxial loading. *Adv. Funct. Mater.* **23**, 5056–5061. (doi:10.1002/adfm.201300402)
6. Bortot E. 2017 Analysis of multilayer electro-active spherical balloons. *J. Mech. Phys. Solids* **101**, 250–267. (doi:10.1016/j.jmps.2017.02.001)
7. Lee DY *et al.* 2022 A wearable textile-embedded dielectric elastomer actuator haptic display. *Soft Robot.* **9**, 1186–1197. (doi:10.1089/soro.2021.0098)
8. Zhu J, Stoyanov H, Kofod G, Suo Z. 2010 Large deformation and electromechanical instability of a dielectric elastomer tube actuator. *J. Appl. Phys.* **108**, 074113. (doi:10.1063/1.3490186)
9. Su Y, Wu B, Chen W, Lü C. 2018 Optimizing parameters to achieve giant deformation of an incompressible dielectric elastomeric plate. *Extr. Mech. Lett.* **22**, 60–68. (doi:10.1016/j.eml.2018.05.004)
10. Li T, Keplinger C, Baumgartner R, Bauer S, Yang W, Suo Z. 2013 Giant voltage-induced deformation in dielectric elastomers near the verge of snap-through instability. *J. Mech. Phys. Solids* **61**, 611–628. (doi:10.1016/j.jmps.2012.09.006)
11. Godaba H, Foo CC, Zhang ZQ, Khoo BC, Zhu J. 2014 Giant voltage-induced deformation of a dielectric elastomer under a constant pressure. *Appl. Phys. Lett.* **105**, 112901. (doi:10.1063/1.4895815)
12. Chen G. 1999 *Controlling chaos and bifurcations in engineering systems*. Boca Raton, FL: CRC Press.
13. Pang W *et al.* 2020 Electro-mechanically controlled assembly of reconfigurable 3D mesostructures and electronic devices based on dielectric elastomer platforms. *Nat. Sci. Rev.* **7**, 342–354. (doi:10.1093/nsr/nwz164)
14. Xu F, Fu C, Yang Y. 2020 Water affects morphogenesis of growing aquatic plant leaves. *Phys. Rev. Lett.* **124**, 038003. (doi:10.1103/PhysRevLett.124.038003)
15. Haughton DM, Ogden RW. 1978 On the incremental equations in non-linear elasticity—II. Bifurcation of pressurized spherical shells. *J. Mech. Phys. Solids* **26**, 111–138. (doi:10.1016/0022-5096(78)90017-0)
16. Haughton DM. 1980 Post-bifurcation of perfect and imperfect spherical elastic membranes. *Int. J. Solids Struct.* **16**, 1123–1133. (doi:10.1016/0020-7683(80)90067-0)
17. DeBotton G, Bustamante R, Dorfmann A. 2013 Axisymmetric bifurcations of thick spherical shells under inflation and compression. *Int. J. Solids Struct.* **50**, 403–413. (doi:10.1016/j.ijsolstr.2012.10.004)
18. Alibakhshi A, Chen W, Destrade M. 2023 Nonlinear vibration and stability of a dielectric elastomer balloon based on a strain-stiffening model. *J. Elast.* **153**, 533–548. (doi:10.1007/s10659-022-09893-5)
19. Jin X, Huang Z. 2017 Random response of dielectric elastomer balloon to electrical or mechanical perturbation. *J. Intell. Mater. Syst. Struct.* **28**, 195–203. (doi:10.1177/1045389X16649446)
20. Sharma AK, Arora N, Joglekar MM. 2018 DC dynamic pull-in instability of a dielectric elastomer balloon: an energy-based approach. *Proc. R. Soc. A* **474**, 20170900. (doi:10.1098/rspa.2017.0900)
21. Liang X, Cai S. 2015 Shape bifurcation of a spherical dielectric elastomer balloon under the actions of internal pressure and electric voltage. *J. Appl. Mech.* **82**, 101002. (doi:10.1115/1.4030881)
22. Xie Y, Liu J, Fu Y. 2016 Bifurcation of a dielectric elastomer balloon under pressurized inflation and electric actuation. *Int. J. Solids Struct.* **78**, 182–188. (doi:10.1016/j.ijsolstr.2015.08.027)
23. Rudykh S, Bhattacharya K, DeBotton G. 2012 Snap-through actuation of thick-wall electroactive balloons. *Int. J. Non-Linear Mech.* **47**, 206–209. (doi:10.1016/j.ijsolstr.2011.05.006)
24. Dorfmann L, Ogden RW. 2014 Nonlinear response of an electroelastic spherical shell. *Int. J. Eng. Sci.* **85**, 163–174. (doi:10.1016/j.ijsolstr.2014.09.001)
25. Mao R, Wu B, Carrera E, Chen W. 2019 Electrostatically tunable small-amplitude free vibrations of pressurized electro-active spherical balloons. *Int. J. Non-Linear Mech.* **117**, 103237. (doi:10.1016/j.ijsolstr.2019.103237)
26. Melnikov A, Dorfmann L, Ogden RW. 2020 Bifurcation of finitely deformed thick-walled electroelastic spherical shells subject to a radial electric field. *Int. J. Non-Linear Mech.* **121**, 103429. (doi:10.1016/j.ijsolstr.2020.103429)

27. Kumar A, Khurana A, Patra AK, Agrawal Y, Joglekar MM. 2023 Electromechanical performance of dielectric elastomer composites: modeling and experimental characterization. *Compos. Struct.* **320**, 117130. (doi:10.1016/j.compstruct.2023.117130)
28. Su Y, Wu B, Chen W, Michel D. 2020 Pattern evolution in bending dielectric-elastomeric bilayers. *J. Mech. Phys. Solids* **136**, 103670. (doi:10.1016/j.jmps.2019.07.013)
29. Bertoldi K, Gei M. 2011 Instabilities in multilayered soft dielectrics. *J. Mech. Phys. Solids* **59**, 18–42. (doi:10.1016/j.jmps.2010.10.001)
30. Atashipour S, Sburlati R. 2016 Electro-elastic analysis of a coated spherical piezoceramic sensor. *Compos. Struct.* **156**, 399–409. (doi:10.1016/j.compstruct.2015.07.012)
31. Dorfmann L, Ogden RW. 2014 *Nonlinear theory of electroelastic and magnetoelastic interactions*, vol. 1. New York, NY: Springer.
32. Hutchinson JW, Miles JP. 1974 Bifurcation analysis of the onset of necking in an elastic/plastic cylinder under uniaxial tension. *J. Mech. Phys. Solids* **22**, 61–71. (doi:10.1016/0022-5096(74)90014-3)
33. Hill R, Hutchinson JW. 1975 Bifurcation phenomena in the plane tension test. *J. Mech. Phys. Solids* **23**, 239–264. (doi:10.1016/0022-5096(75)90027-7)
34. Zurlo G, Destrade M, DeTommasi D, Puglisi G. 2017 Catastrophic thinning of dielectric elastomers. *Phys. Rev. Lett.* **118**, 078001. (doi:10.1103/PhysRevLett.118.078001)
35. Bortot E, Shmuel G. 2018 Prismatic bifurcations of soft dielectric tubes. *Int. J. Eng. Sci.* **124**, 104–114. (doi:10.1016/j.ijengsci.2017.11.002)
36. Dorfmann A, Ogden RW. 2010 Electroelastic waves in a finitely deformed electroactive material. *IMA J. Appl. Math.* **75**, 603–636. (doi:10.1093/imamat/hxq022)
37. Martin P. 2020 A Stroh formalism for small-on-large problems in spherical polar coordinates. *J. Elast.* **138**, 125–144. (doi:10.1007/s10659-019-09730-2)
38. Norris AN, Shuvalov AL. 2010 Wave impedance matrices for cylindrically anisotropic radially inhomogeneous elastic solids. *Q. J. Mech. Appl. Math.* **63**, 401–435. (doi:10.1093/qjmam/hbq010)
39. Gent AN, Cho IS. 1999 Surface instabilities in compressed or bent rubber blocks. *Rubber Chem. Technol.* **72**, 253–262. (doi:10.5254/1.3538798)
40. Zhao X, Suo Z. 2007 Method to analyze electromechanical stability of dielectric elastomers. *Appl. Phys. Lett.* **91**, 061921. (doi:10.1063/1.2768641)
41. Kim B, Lee SB, Lee J, Cho S, Park H, Yeom S, Park SH. 2012 A comparison among Neo-Hookean model, Mooney-Rivlin model, and Ogden model for chloroprene rubber. *Int. J. Precis. Eng. Manuf.* **13**, 759–764. (doi:10.1007/s12541-012-0099-y)
42. Bustamante R, Dorfmann A, Ogden RW. 2008 Nonlinear electroelastostatics: a variational framework. *Z. Angew. Math. Phys.* **60**, 154–177. (doi:10.1007/s00033-007-7145-0)
43. Riccobelli D, Ciarletta P. 2017 Shape transitions in a soft incompressible sphere with residual stresses. *Math. Mech. Solids* **23**, 1507–1524. (doi:10.1177/1081286517747669)
44. Logg A, Mardal KA, Wells G. 2012 *Automated solution of differential equations by the finite element method: the FEniCS book*, vol. 84. Berlin, Germany: Springer Science & Business Media.
45. Seydel R. 2009 *Practical bifurcation and stability analysis*, vol. 5. Berlin, Germany: Springer Science & Business Media.
46. Alnæs MS, Logg A, Ølgaard KB, Rognes ME, Wells GN. 2014 Unified form language: a domain-specific language for weak formulations of partial differential equations. *ACM Trans. Math. Softw.* **40**, 1–37. (doi:10.1145/2566630)
47. Riccobelli D, Noselli G, DeSimone A. 2021 Rods coiling about a rigid constraint: helices and perversions. *Proc. R. Soc. A* **477**, 20200817. (doi:10.1098/rspa.2020.0817)
48. Emam SA, Eltaher MA, Khater ME, Abdalla WS. 2018 Postbuckling and free vibration of multilayer imperfect nanobeams under a pre-stress load. *Appl. Sci.* **8**, 2238. (doi:10.3390/app8112238)
49. Plante JS, Dubowsky S. 2006 Large-scale failure modes of dielectric elastomer actuators. *Int. J. Solids Struct.* **43**, 7727–7751. (doi:10.1016/j.ijsolstr.2006.03.026)
50. Stark KH, Garton CG. 1955 Electric strength of irradiated polythene. *Nature* **176**, 1225–1226. (doi:10.1038/1761225a0)
51. Su Y, Riccobelli D, Chen Y, Chen W, Ciarletta P. 2023 Tunable morphing of electroactive dielectric-elastomer balloons. Figshare. (doi:10.6084/m9.figshare.c.6764173)